



LAWRENCE
LIVERMORE
NATIONAL
LABORATORY

Fabrication of Planar Laser Targets with Sub-Micrometer Thickness Uniformity

M. Bono, C. Castro, L. Griffith, R. Hibbard, J.
Kass, J. Satcher

September 7, 2005

2005 Tri-Lab Engineering Conference
Monterey, CA, United States
September 12, 2005 through September 15, 2005

Disclaimer

This document was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor the University of California nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or the University of California, and shall not be used for advertising or product endorsement purposes.

Fabrication of Planar Laser Targets with Sub-Micrometer Thickness Uniformity

The Cu EOS Targets

**Presented to:
2005 Tri-Lab Engineering Conference**

September 12-15, 2005




**Matthew Bono, Carlos Castro, Lee Griffith, Robin Hibbard,
Jeff Kass, Joe Satcher**

**This work was performed under the auspices of the U.S. Department of Energy by the University of California
Lawrence Livermore National Laboratory under Contract No. W-7405-Eng-48.**


Lawrence Livermore National Laboratory, P.O. Box 808, Livermore, CA 94551

The selection of target specifications requires close collaboration between Target Fab and Physics

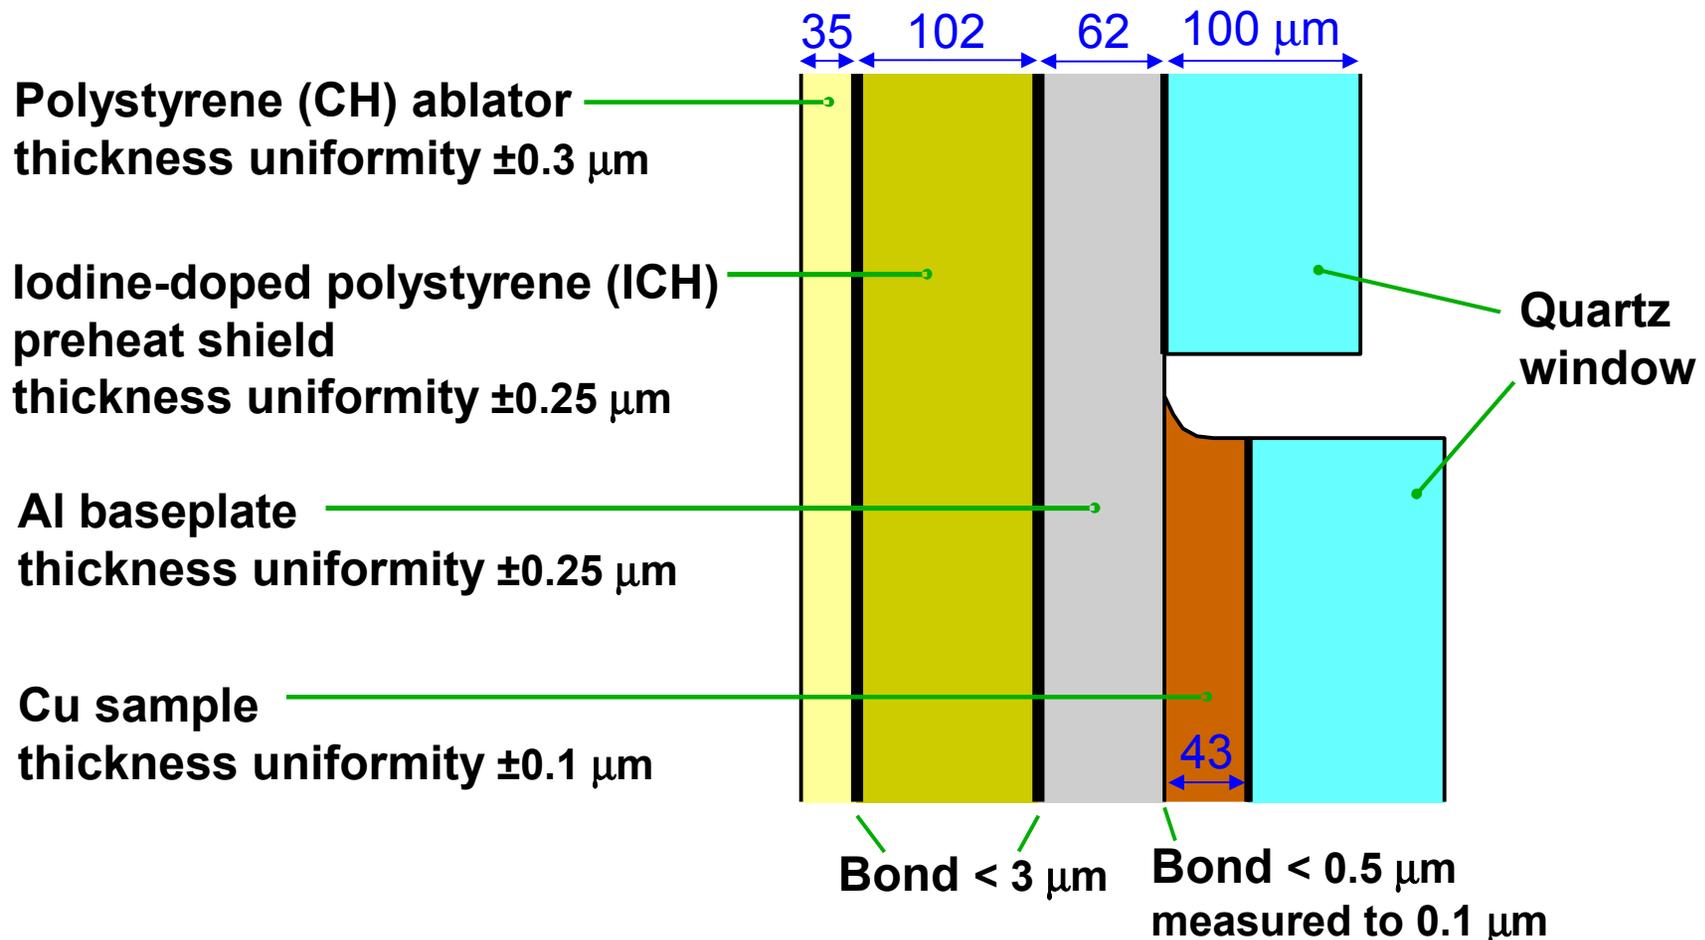

To make the targets manufacturable, the specifications were re-examined and revised several times.

The target specifications necessitate a very precise manufacturing strategy

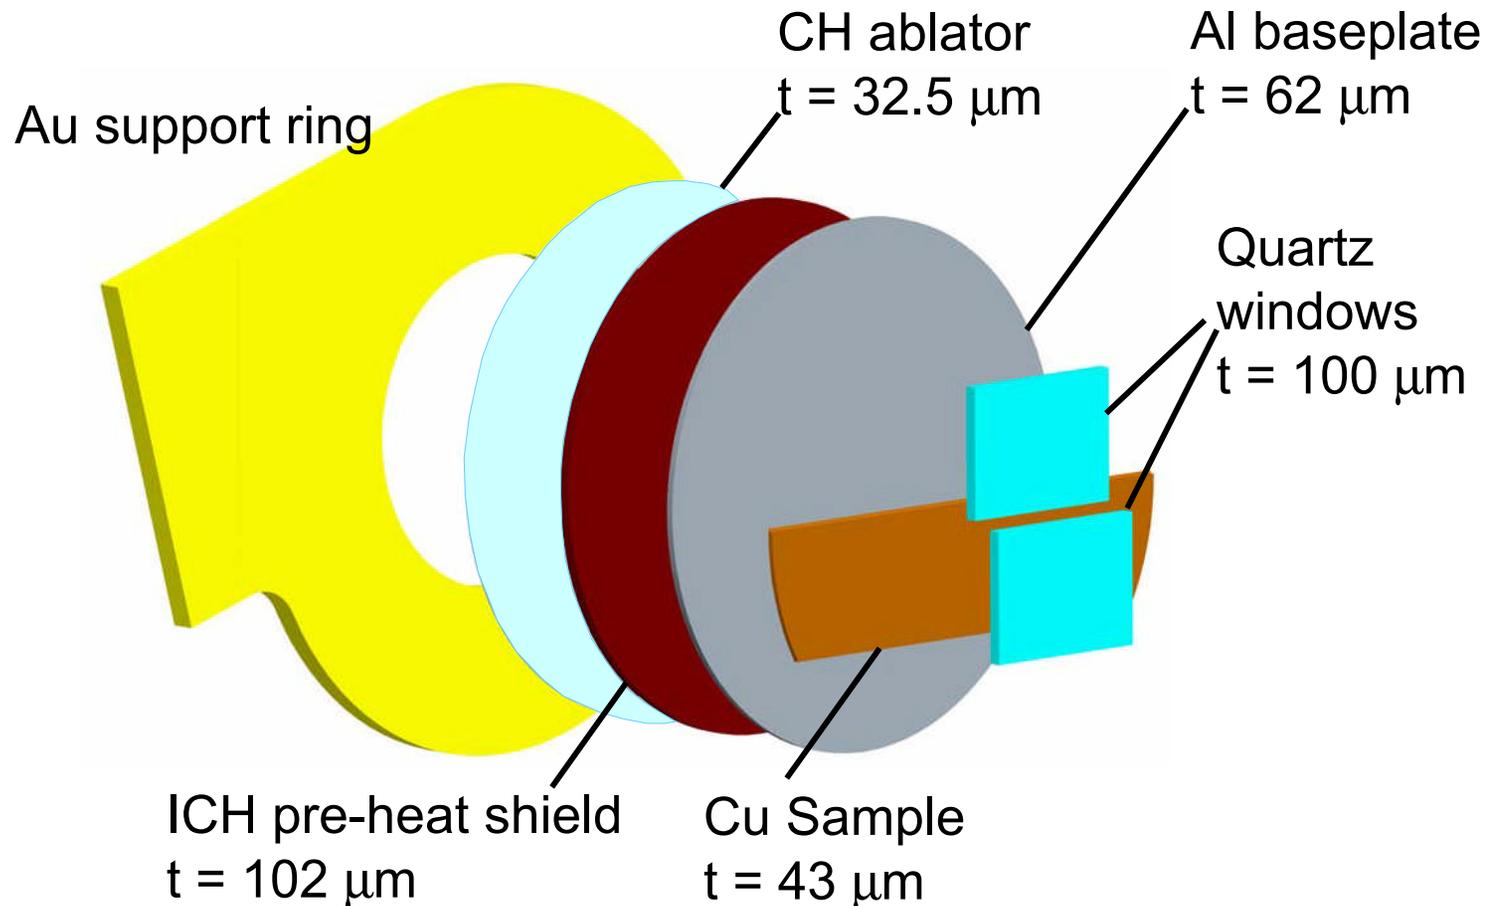


The required level of precision is approximately
10× that of most laser targets

The specified thickness uniformities of the components require high-precision fixturing methods



A batch of targets is built on a 6 mm thick 100 mm diameter Al disk. Both sides of the disk are diamond turned so that the faces are parallel to 0.1-0.2 μm .

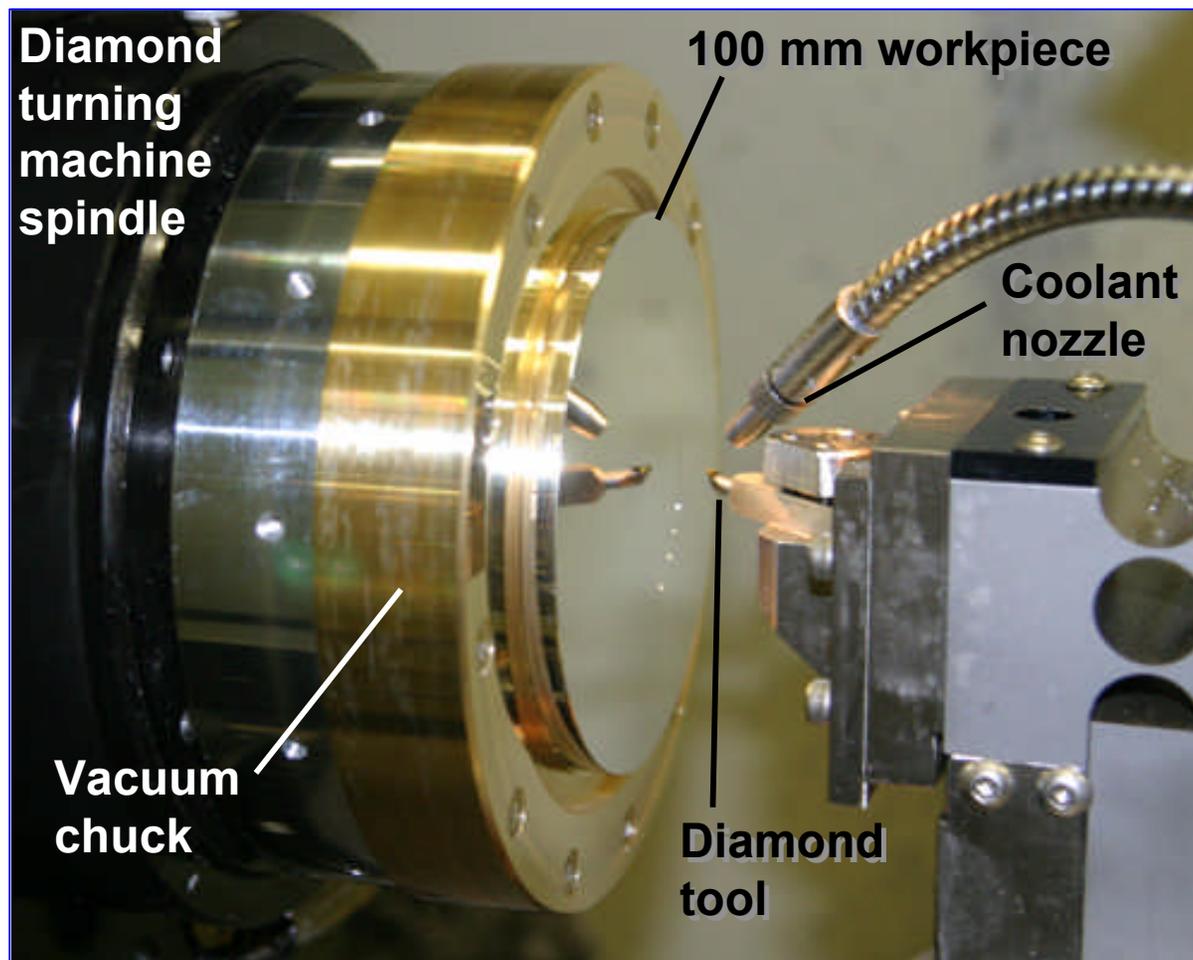

To meet the specifications for the baseplate-sample joint, the Cu sample is deposited onto the Al baseplate



The requirements for the Cu-Al interface are very demanding.

- Cu-Al interface must be $< 0.1 \mu\text{m}$
- Outside the $25 \mu\text{m}$ region on either side of the edge of the Cu, all flaws must be $< 0.1 \mu\text{m}$
- Al disk must not be warped, scratched, pitted, or otherwise damaged
- Cu must have adequate adhesion for diamond turning
- Cu must be placed on Al disk in a band with radial tolerance of $\pm 10 \mu\text{m}$


A great deal of research has gone into identifying an acceptable method of depositing Cu onto the Al disk.

The masking process is designed to accommodate flaws created in the electroplating process



The selected deposition process sputters 3-5 μm of Cu onto the Al and then electroplates additional Cu.


The 100 mm Al disk is masked with precisely placed Kapton tape prior to sputtering.

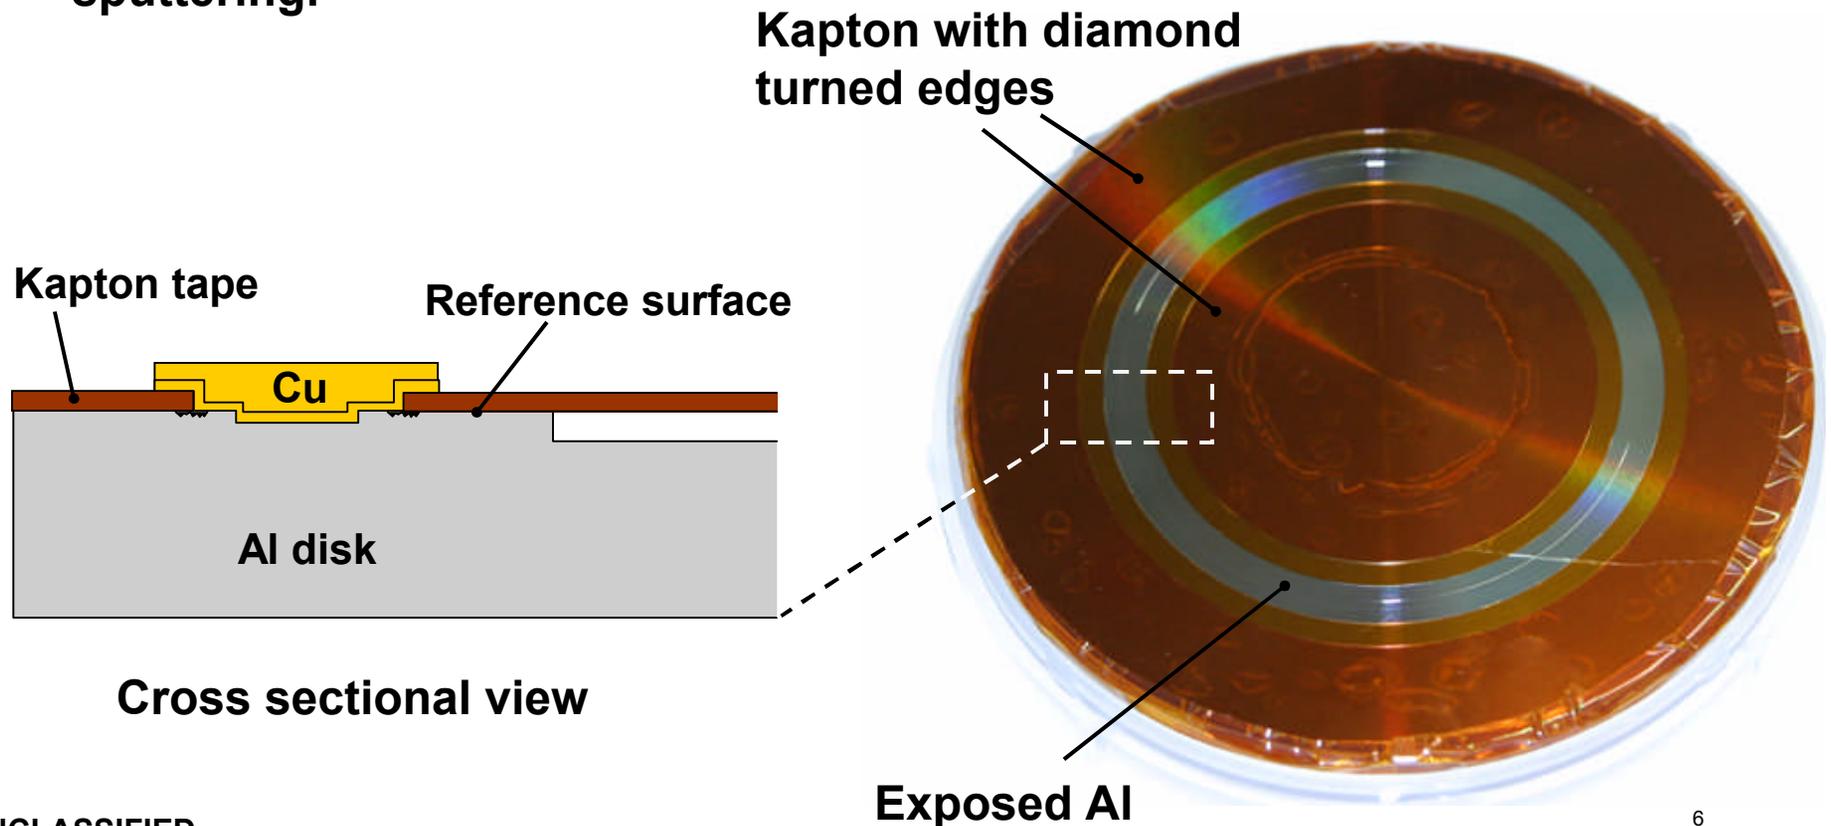

After sputtering 3-5 μm of Cu, additional Cu is electroplated onto the sputtered Cu



Disk masked with Kapton tape after sputtering 3-5 μm of Cu

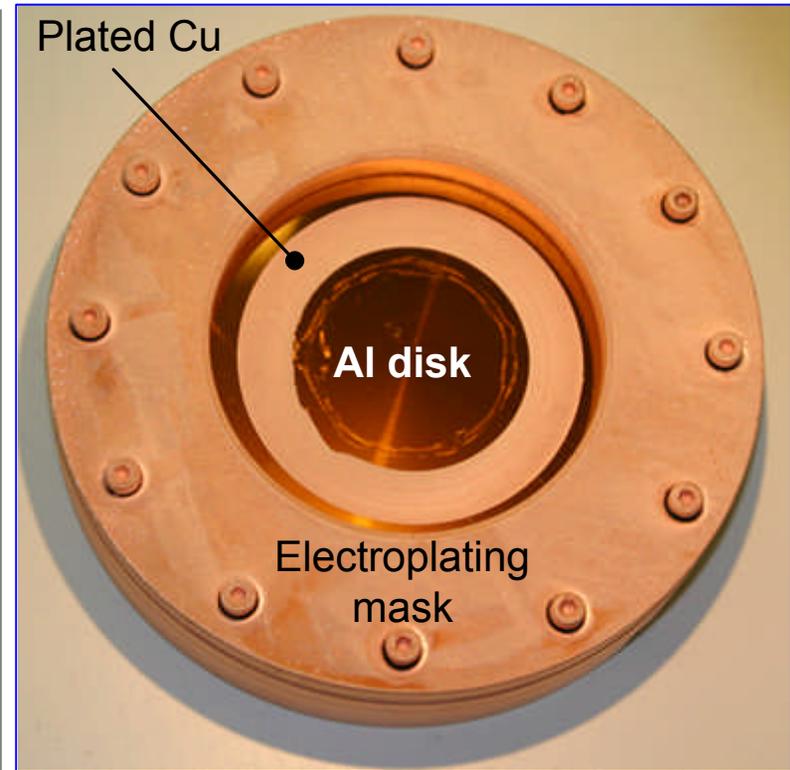


Disk in the hardmask that is used to electroplate additional Cu


The deposited Cu is diamond turned to a thickness of 43 μm



A band of Cu of thickness 43 μm and width 1 mm is left on the surface of the Al.

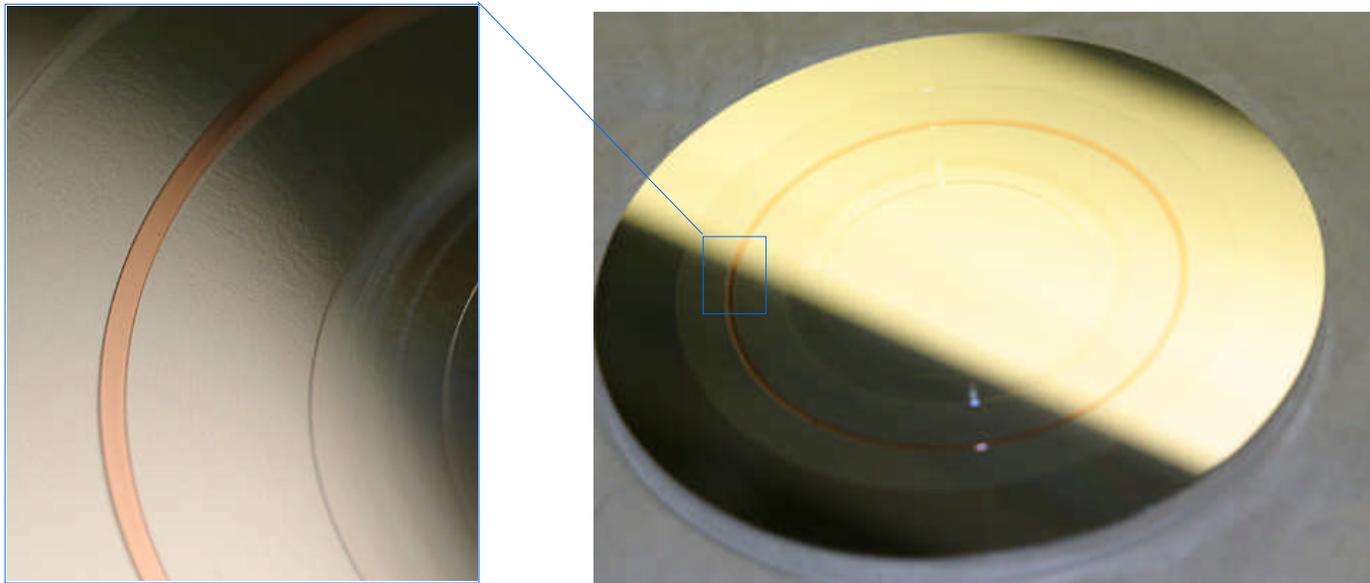

Machining may leave a 1 μm step in the Al, but it must be known to within 0.2 μm

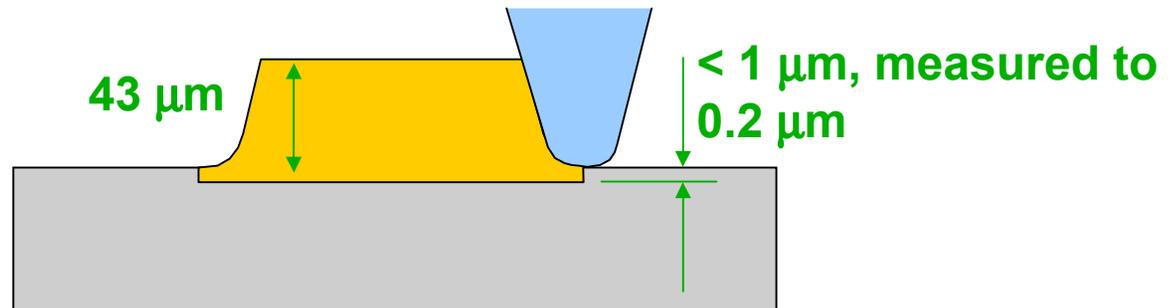


The Cu is then carefully measured in several locations with an LVDT mounted on the machine tool.



The Cu-side of the disk is placed against another precision narrow-land vacuum chuck



Centering guides allow the ring of Cu to fit precisely into a groove in the chuck.

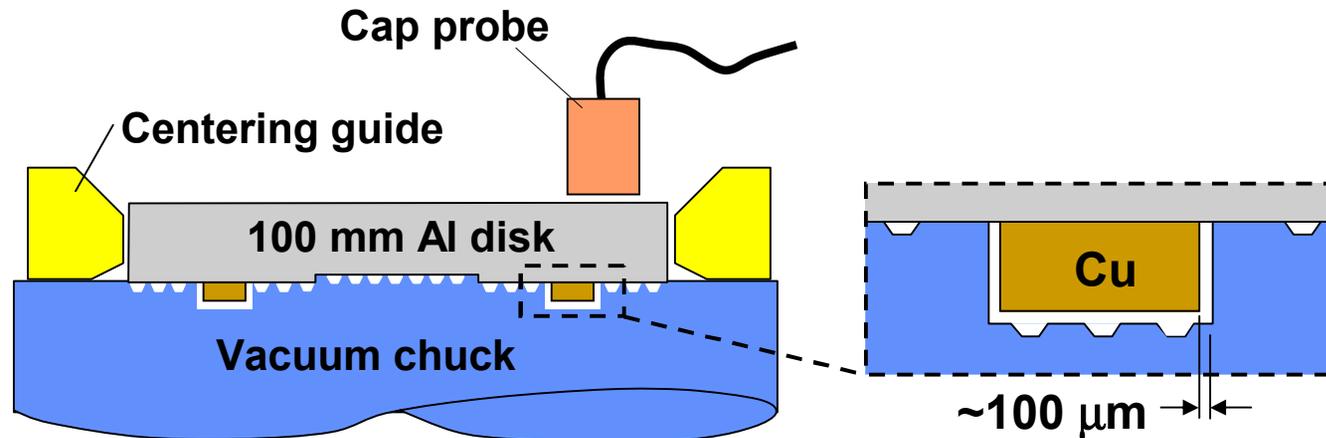


The Al disk is machined to a thickness of $62 \mu\text{m}$ to form the baseplate.

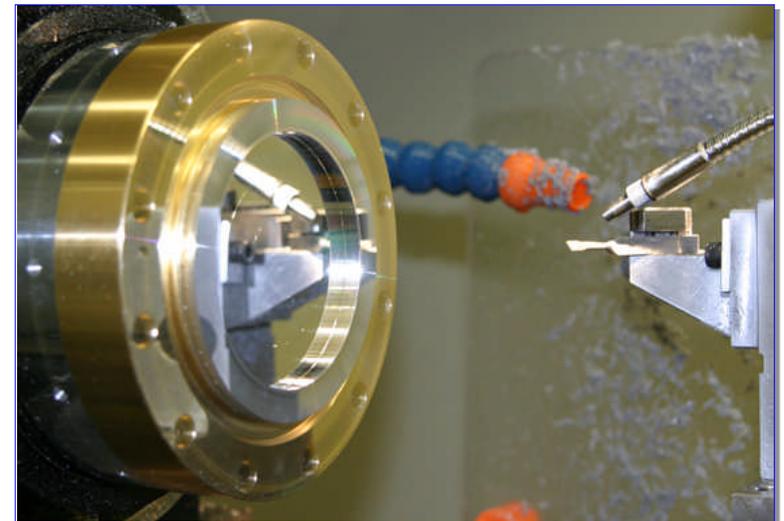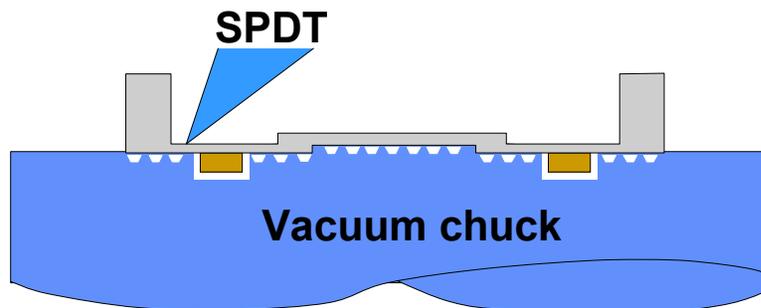


Pads of iodine-doped polystyrene are bonded and machined to form the pre-heat shields



Precise pads of iodine-doped polystyrene (ICH) are bonded to the Al using a special assembly station.

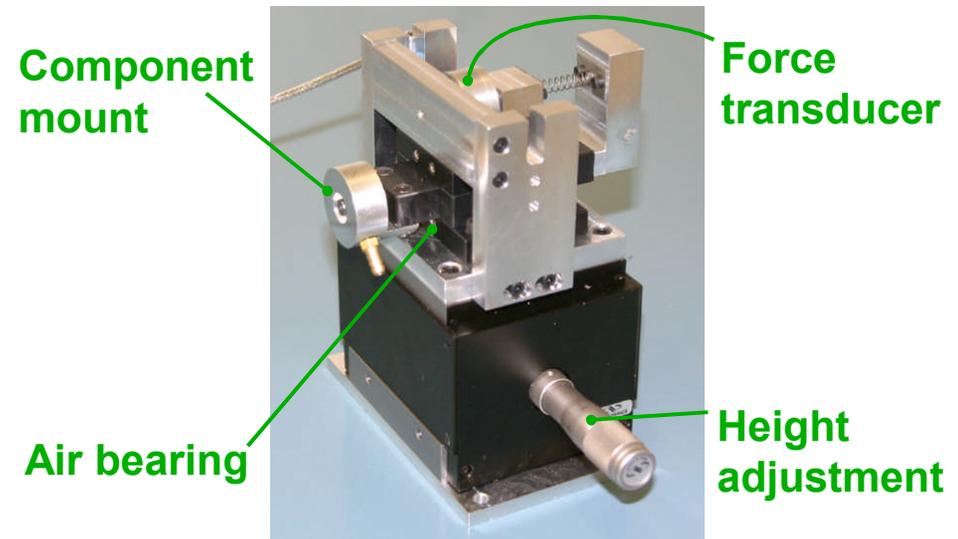

An LVDT measures the thickness of the adhesive in 4 spots.

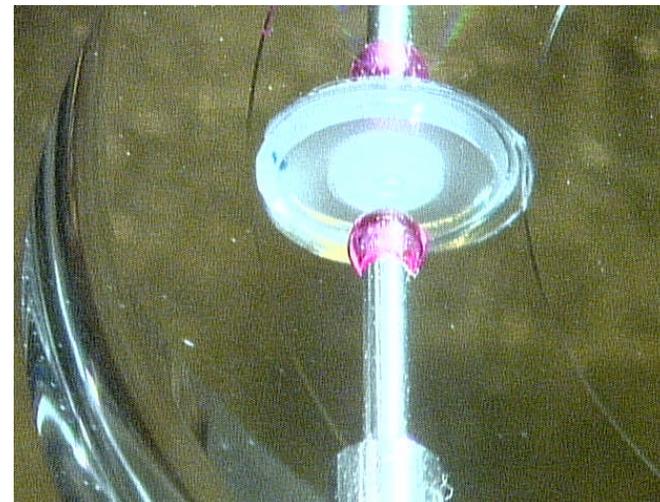



After finishing the pre-heat shields, pads of polystyrene are bonded and machined to form the ablators




The pads of iodine-doped polystyrene are diamond turned to the required thickness to complete the pre-heat shields.

The pre-heat shields are then measured again with the LVDT in 4 spots.

To form the ablators, the process of bonding, measuring, machining, and measuring is repeated with pads of polystyrene (CH).

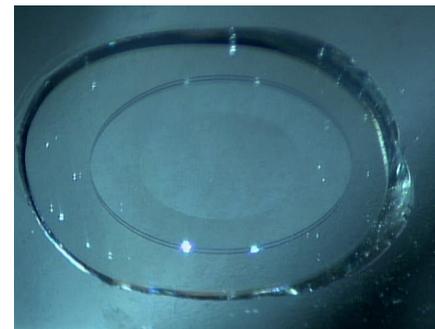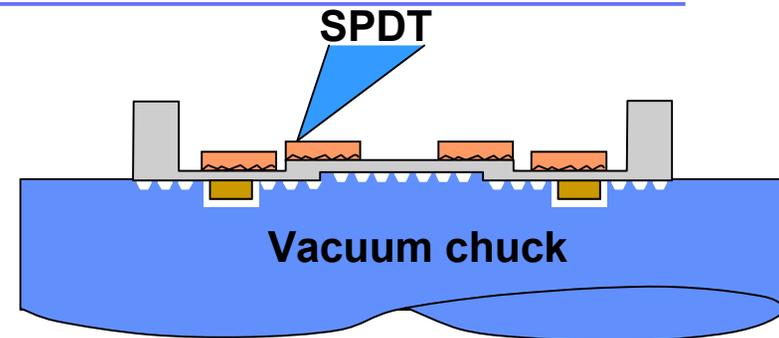



Diamond turned pad

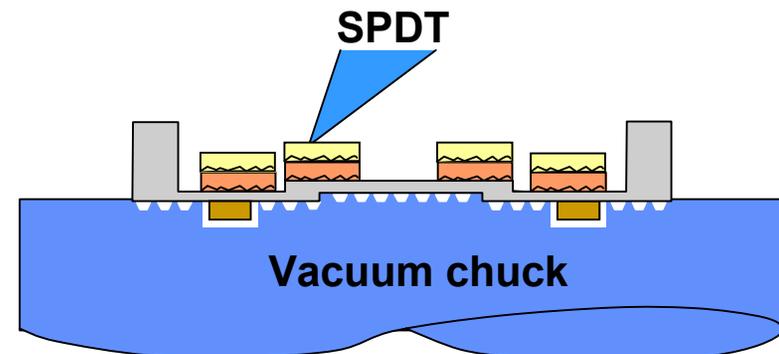

Targets are laser cut from the 100 mm disk and bonded to windows and support rings



The “ablator – preheat shield – baseplate – sample” subassemblies are laser cut from the 100 mm disk

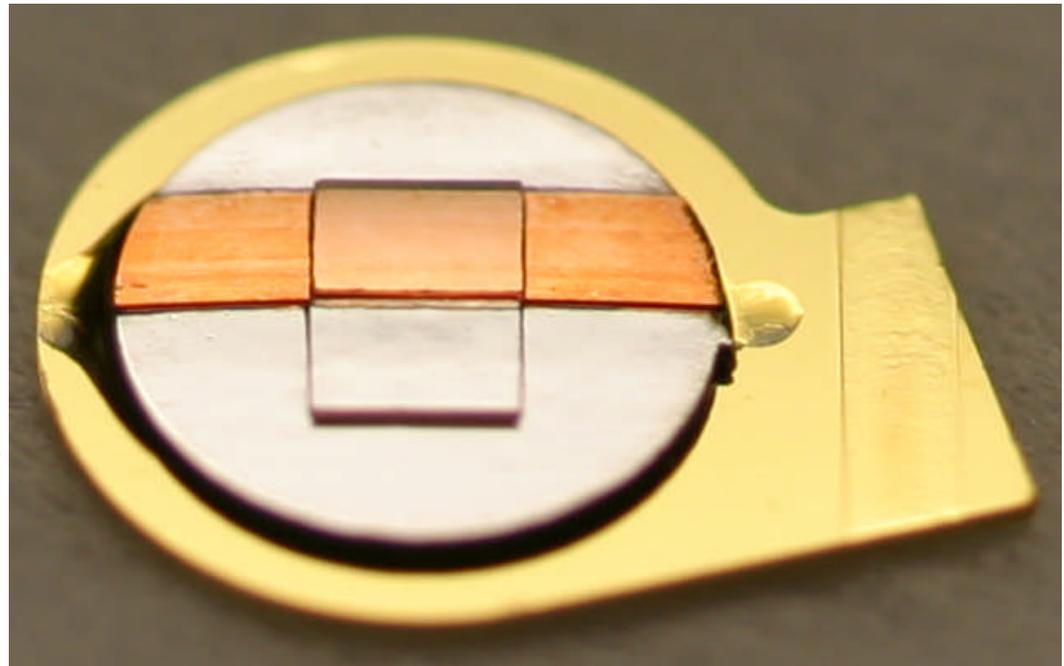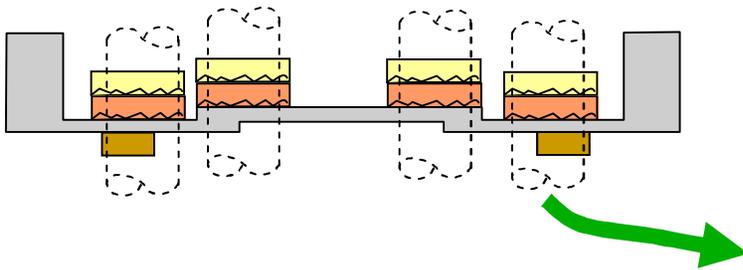

Summary - close collaboration between Target Fab and physicists is crucial to designing manufacturable targets



- **Metrology is almost as labor-intensive as the fabrication process.**
- **The required level of precision is approximately 10× that of most laser targets. Extreme care must be taken at each step of the process.**
- **Appropriate fixturing of the workpiece is critical to achieving the manufacturing and metrology tolerances.**
- **The seating of the workpiece against the vacuum chucks must be verified at each step.**
- **A great deal of research has gone into identifying an acceptable method of depositing Cu onto the Al disk. Sputter-seeded electroplating was identified as an acceptable method of depositing the Cu.**
- **Batch processing allows several targets to be produced from each 100 mm disk.**